

Improvement of Long Term Performance of Temporary and Permanent Traffic Areas Using Composite Geogrid Reinforcement

J. Klomp maker. Bauberatung Geokunststoffe GmbH & Co. KG, Germany. ijklompmaker@bbgeo.com
A. Partridge. NAUE GmbH & Co. KG, Germany. apartridge@naue.com

ABSTRACT

Geosynthetics have over the years made steady progress into the construction industry. The use of Geotextiles and Geogrids in the industry has become well documented. Recently, innovative products which combine both a needlepunched nonwoven geotextile and a laid and welded geogrid (geocomposite) in a single structure have been developed and this paper will discuss the recent testing that has been carried out on such a product with regard to its benefit in road construction. This could have a beneficial effect for Africa where improved transport links could have a major part to play in the improved prosperity of the continent. The test results show that the composite material can provide a tremendous increase in long term trafficability compared to roads constructed without reinforcement or only with the use of a geogrid or a separately installed geogrid and separator geotextile. This paper will discuss the testing that has taken place and will explain why these materials perform differently. Finally two international case studies are presented, where these geocomposite products have been used.

1. INTRODUCTION

1.1 General

Container storage areas carry large traffic volumes and typically have concrete or paved surfacing over a base layer of aggregate. The combined surface and base layers act together to support and distribute traffic loading to the subgrade. Problems are usually encountered when the subgrade consists of soft clays, silts and organic soils. These types of soils are often water sensitive and, when wet, unable to adequately support traffic loads. If unimproved, the subgrade will mix with the road base aggregate, which leads to a reduction of strength, stiffness and drainage characteristics, promoting distress and early failure of the roadway. Contamination with fines makes the base course more susceptible to frost heaving.

1.2 Separation of Subgrade and base course

A geotextile which is placed between the subgrade and the base course layer provides physical separation of subgrade and base materials during construction and during operating life of the trafficked area (see Figure 1).

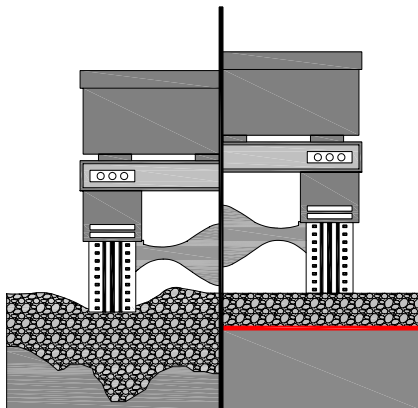


Figure 1. Illustration of geotextile separation function

The separation function of the geotextile is defined by a prevention of mixing, where mixing is caused by mechanical actions. The mechanical actions generally arise from physical forces imposed by construction or operating traffic and may cause the aggregate to be pushed down into the soft subgrade and / or the subgrade to be squeezed up into the base aggregate. A properly designed geotextile separator allows the base aggregate to remain "clean", which preserves its strength and drainage characteristics. The use of geotextile separators ensures that the base course layer in its entirety will contribute and continue to contribute its structural support of vehicular loads; the separator itself is not viewed to contribute structural support to the aggregate layer. Yoder and Witczak (1975) state that as little as 20% by weight of the subgrade mixed in with the base aggregate will reduce the bearing capacity of the aggregate to that of the subgrade. This highlights the importance of a geotextile separator with regard to the performance of base aggregate layers on fine-grained subgrades.

1.3 Reinforcement of base courses using geogrid reinforcement

Vehicular loads applied to the surface of trafficked areas create a lateral spreading motion of the unbound aggregate layers. Tensile lateral strains are created at the interface subgrade/geogrid as the aggregate moves down and sideways due to the applied load. Through shear interaction of the base aggregate with the geogrid, a.k.a. inter-locking, (see Figure 2), the aggregate is laterally restrained or confined (see Figure 3) and tensile forces are transmitted from the aggregate to the geogrid.

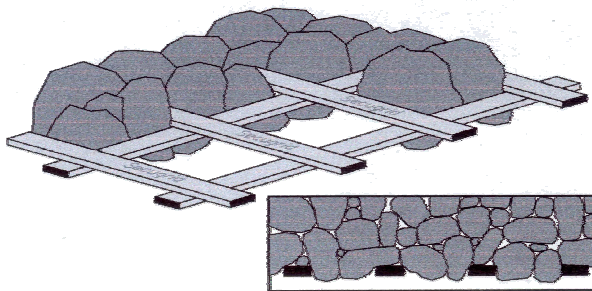


Figure 2. Interaction of aggregate with geogrid

As the geogrid is much stiffer in tension as the aggregate itself, the lateral stress is reduced in the reinforced base aggregate and less vertical deformation at the road surface can be expected. This interaction between geogrid and base course material increases the shear strength and thus the load distribution capacity of the used base course material.



Figure 3. Lateral restraint of aggregate using high modulus laid and welded geogrids

The increased load distribution capacity reduces vertical stresses on the subgrade, which finally reduces the deformation (rutting) on the surface of the aggregate layer. This correlation enables the reduction of reinforced base course thicknesses in comparison to un-reinforced layers (see Figure 4).

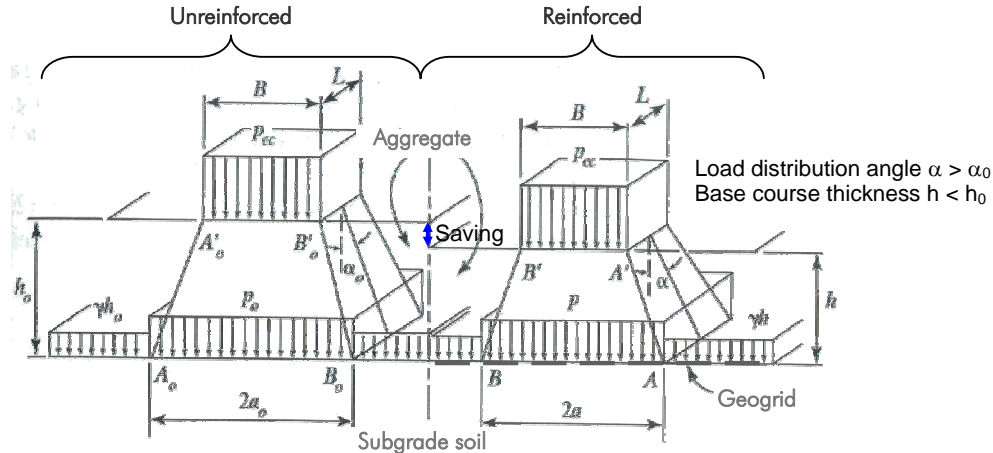


Figure 4. Increase of load distribution capacity with the use of geogrids (Giroud & Noiray 1981)

In many projects, good quality base course aggregate is not available on site or close to the site. As a result, high transport costs of imported, expensive good quality base aggregate have a great influence on the total project costs. Especially under those conditions geosynthetic reinforcement and separation products can help to save money by reducing the amount of imported fill material needed to achieve the specified bearing capacity for the expected loads on the base course.

To combine the function of reinforcement and separation in one product, so called Geocomposites have been developed. Geocomposites (see Figure 5) allow faster construction rates compared to separately installed geogrid and geotextile components.



Figure 5. Geocomposite (geogrid reinforcement & needle punched nonwoven geotextile, firmly bonded between the cross laid reinforcement bars)

2. PERFORMANCE OF BASE REINFORCEMENT GEOGRIDS IN ROADWAY STABILIZATION APPLICATIONS

2.1 Large Scale Laboratory Test

The purpose of the study was to evaluate the reinforcement benefit provided by different geogrids. Benefit was defined in terms of the number of load cycles to reach a specific permanent rut depth of approx. 75 mm in the aggregate surface layer for each section and Traffic Benefit Ratio (TBR), which is the number of load cycles for a reinforced section divided by the number of load cycles to reach this same rut depth for a comparable unreinforced test section. The test sections were instrumented to measure geosynthetic deformation and subgrade pore water pressure response.

The pavement test box facility used for the laboratory test was designed and constructed for the purpose of conducting laboratory, full-scale experiments on reinforced and unreinforced pavement sections and it meets the requirements of specifications developed for AASHTO Subcommittee 4E as

contained in Berg et al., 2000. The test box facility is designed to mimic pavement layer materials, geometry and loading conditions encountered in the field as realistically as possible with an indoor, laboratory based facility. This type of test box facility allows a high degree of control to be exercised on the construction and control of pavement layer material properties. Each roadway test section was constructed with a nominal cross-section consisting of 300 mm of base course aggregate and 1.1 m of subgrade soil with a CBR = 1. The geosynthetic was placed between the base course and subgrade layers. A control test section having the same cross section without a geogrid was used for comparison to the geogrid stabilized sections. A cyclic, non-moving load with a peak load value of 40 kN was used to mimic dynamic wheel loads. Sensors were used to measure applied pavement load, pavement surface deformation, and stress and strain in the base aggregate and subgrade soils. At a later state, the results of the dynamic plate loading laboratory tests shall be compared to results from test sections in the field, where moving wheel loads (three axle dump truck) are used to generate the pre-defined deformation rates. In both, the laboratory and the field test, the boundary conditions of the prepared subgrade and base course (as e.g. type, moisture content, gradation & angularity of base) are comparable. Amongst others, the results shall be used to quantify the influence of circular (plate load) versus biaxial loading (wheel load) on the development of rut deformation.

2.2 Test-Box and Loading Apparatus

Test sections were constructed in a 2 m by 2 m by 1.5 m deep box shown in Figure 6. The walls of the box consist of 150 mm thick reinforced concrete. The front wall is removable in order to facilitate excavation of the test sections.

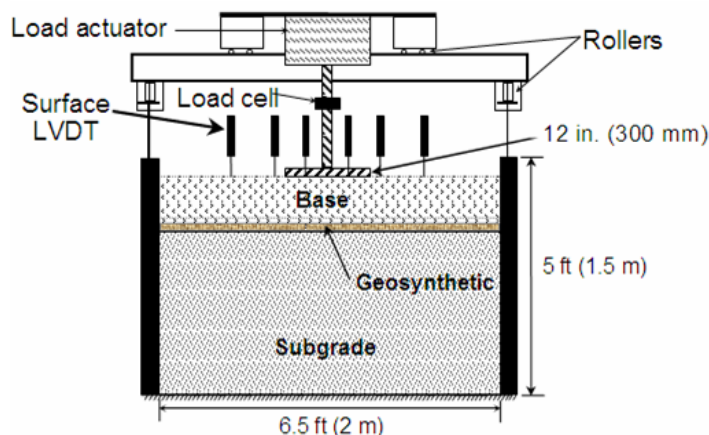


Figure 6. Schematic diagram of the pavement test facility

I-beams set into two of the concrete walls serve as a base for the loading frame. The load frame consists of two additional I-beams that span and react against the I-beams set into the concrete walls of the box. A load actuator, consisting of a pneumatic cylinder with a 300-mm diameter bore and a stroke of 75 mm, is placed between the two I-beams of the frame. A 50 mm diameter steel rod extends from the piston of the actuator. The rod is rounded at its tip and fits into a cup welded on top of the load plate that rests on the pavement surface.

The load plate consists of a 300 mm diameter steel plate with a thickness of 25 mm. A 6.4 mm thick, waffled butyl-rubber pad is placed beneath the load plate in order to provide a uniform pressure and avoid stress concentrations along the plate's perimeter. Figure 2 shows an image of the load plate resting on the pavement surface. A binary solenoid regulator attached to a computer controls the load-time history applied to the plate. The software controlling the solenoid is the same software used to collect data from the pavement sensors. The software is set up to provide a linear load increase from zero to 20 kN over a 0.3 second rise time, followed by a 0.2 second period where the load is held constant, followed by a load decrease to zero over a 0.3 second period and finally followed by a 0.5 second period of zero load before the load cycle is repeated, resulting in a load pulse frequency of 0.67

Hz. The maximum applied load of 40 kN resulted in a pavement pressure of 550 kPa. This load represents one-half of an axle load from an equivalent single axle load (ESAL).

Instrumentation was included in each test section. The instrumentation is designed to evaluate rutting in the stabilization aggregate, strain distribution in the reinforcement with distance away from the wheel load, and pore water pressure response of the subgrade during placement, compaction and subsequent loading. Instrumentation was included to make the following measurements:

1. Vertical surface deformation in the stabilization aggregate layer.
2. Applied load to the plate using a calibrated load cell.
3. Pore pressure in the subgrade during construction and pavement loading.
4. The geosynthetics were instrumented with wire extensometers, which were connected to LVDTs to measure the transfer of stress away from the wheel loading area.
5. The geosynthetics were extended through the front of the test box and visually monitored to determine if any movement was occurring at the edge of the box during application of the load.

2.3 Geosynthetic Materials

The geosynthetic materials used in these tests were a welded polypropylene biaxial geogrid and a composite geogrid using a welded polypropylene biaxial geogrid where a needle punched nonwoven geotextile is firmly bonded between the cross laid reinforcement bars. Tests were also performed with the welded polypropylene geogrid placed directly over a needlepunched nonwoven polypropylene separation geotextile (NP NW GTX). The used geotextile had a mass per unit area of 150 g/m². The relevant properties of the used materials are shown in Table 1.

Table 1. Geogrid Characteristics

Properties	Laid and welded PP geogrid (30 kN/m) (LW GG30)	Laid and welded PP geogrid (60 kN/m) (LW GG60)	Geocomposite material of laid and welded PP geogrid (30 kN/m) + PP nonwoven GTX (GC GG30)
T _{ult} MD (kN/m)	2055	3080	2060
T _{ult} XD (kN/m)	2055	3080	2060
T _{2%} XD (kN/m)	686	1850	690
T _{2%} XD (kN/m)	686	1850	690

2.4 Subgrade Soil

Piedmont silt (ML-MH) from Georgia was used for the subgrade. The residual soil was selected based on its problematic construction characteristics that include pumping and weaving at near optimum moisture contents, which usually requires chemical or mechanical stabilization, especially when wet of optimum (as is most often the case). Residual soils tend to retain the parent rock structure (e.g., joints and fractures) with additional fractures occurring due to stress relief during excavation. Excess water collected in this structure results in high sensitivity when disturbed. These soils are also often characterized by a relatively fast dissipation of pore water pressure as opposed to more cohesive soils. The gradation tests (ASTM 422 and ASTM 1140) indicate that the soil is micaceous sandy silt (ML-MH) with 95% passing a 1mm sieve and 65% passing a 0.075 mm sieve. The soil has a maximum dry unit weight of about 15.2 kN/m³ at an optimum moisture content of 17%.

2.5 Base Course Aggregate

The base course material used in all test section was a graded aggregate base meeting the Georgia Department of Transportation specifications. Standard Proctor compaction test (ASTM D 698) and gradation tests were performed on the aggregate base course and the results are also included in

Appendix A. The gradation test results on the aggregate base indicate that it meets the Georgia Department of Transportation specifications for base course materials. The aggregate has a maximum dry density of about 22.8 kN/m^3 at an optimum moisture content of 5.4%. The graded aggregate base was estimated to have a friction angle of 43° based on large direct shear tests that have been previously performed on similar materials at GTX.

2.6 Test Results

The primary results of the stabilization test are in terms of the deformation response of the aggregate layer. Figure 7 provides a summary of the permanent deformation response for all test sections constructed with 12 inches of aggregate and a CBR = 1%. Table 2 provides a comparison of the performance characteristics from each test section, including the number of cycles and the corresponding Traffic Benefit Ratio (TBR) for each of the test result at 25 mm and 75 mm of rutting. Rut depths between 25 mm and 75 mm are acceptable deformation rates for unpaved roads but not for paved roads.

The results clearly show a difference in the performance of the geosynthetics evaluated in the study. The Geocomposite material (laid and welded geogrid (30 kN/m) + nonwoven needlepunched geotextile firmly bonded between the cross laid reinforcement bars) performed the best of all materials tested and reached over 850 cycles of loading before reaching 75 mm of rutting and had a TBR value of over 170. Over 10,000 cycles were required to reach a rut depth of 100 mm. Open geogrids may be at a disadvantage with the type of soil used, as no filter stability between the coarse aggregate and the fine grained subgrade is given, so that the soft subgrade can easily be penetrated by gravel particles from the base course layer until interlock is developed. Regardless, both laid and welded geogrids provided significant improvements in deformation response over the control section with TBR values between 11 and 19.

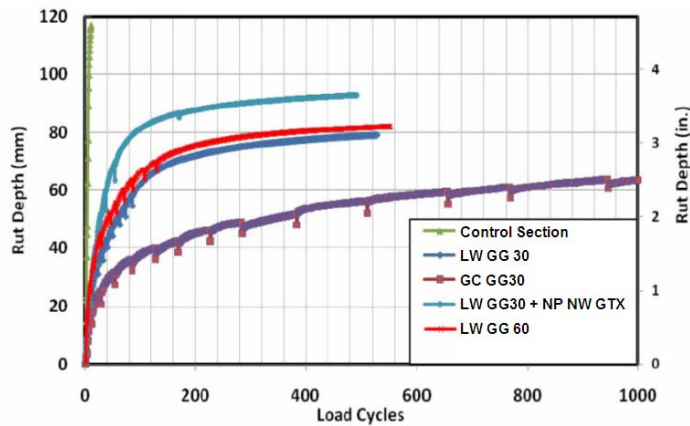


Figure 7. Permanent Deformation Response versus Load Cycles for CBR = 1 Subgrade

Table 2. Performance Characteristics (TBR) of each Test Section

Section	Number of Cycles		Traffic Benefit Ratio (TBR)	
	25mm rut	75mm rut	25mm rut	75mm rut
Control	1.5	5	1	1
LW GG30	4.5	97	3	19.4
LW GG 60	1.5	55	1	11
GC GG30	6.5	855	4.3	171
LW GG30 + NP NW GTX	1.2	31	0.8	6.2

Much of the difference between the two laid and welded geogrids with 30 kN/m and 60 kN/m (LW GG30 & LW GG60) tensile strength can be attributed to the differences in the first few load cycles which are applied at the beginning of the test. As it is not possible to maintain a consistent loading during the application of the first few load cycles movement occurs due to shoving and displacement of aggregate during interlock. In stabilization research performed by the US Army Corps of Engineers, these cycles are referred to as "initial seating" (Tingle and Jersey, 2005) and they are removed from the data. If this procedure is followed and the first 3 cycles are removed, the hierarchy of the data remains the same, however then the deformation response of the 60 kN/m laid and welded geogrid is slightly better (less rutting) compared to the 30 kN/m laid and welded geogrid. The laid and welded geogrid placed over the nonwoven needlepunched geotextile (LW GG30 + NP NW GTX). The higher deformation response of the separately installed components is attributed to sliding of the geogrid over the nonwoven geotextile. A summary of the pore pressure response of each test section is shown in Figure 8. The pore pressure directly corresponds to the results in Figure 7 with the high initial pore pressure developing for test sections where the largest amount of deformation per cycle was measured. The pore water pressure results indicate the disturbance due to aggregate penetration into the subgrade in the control section and the open geogrid section, which leads to high pore water pressure. The increase in pore water pressure reduces the effective strength of the soil, resulting in an undrained subgrade strength that is actually less than CBR = 1% and correspondingly increased rutting occurs. This rapid pore pressure build up does not occur in the Geocomposite (GC GG30) due to the separation provided by the geotextile.

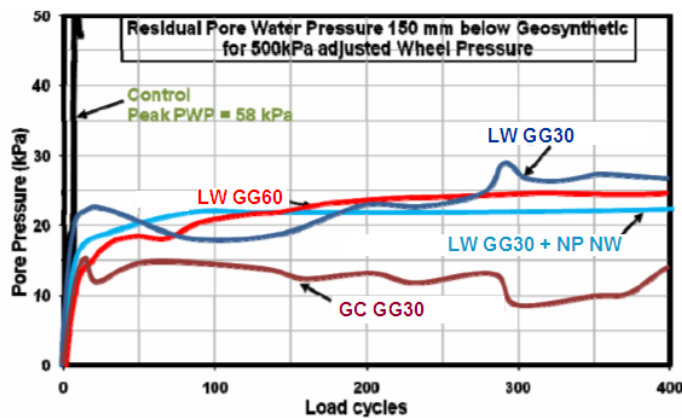


Figure 8. Pore pressure in Subgrade versus Load Cycles for CBR = 1 Subgrade

3. CASE HISTORIES

3.1 Oman Polypropylene LLC Plant at Sohar Port, Sultanate of Oman

Oman Polypropylene LLC started to build its Polypropylene plant at the end of 2004. For the development of the port at Sohar, which is located at the Gulf of Oman, an area of approx. 24 hectares was artificially created by dredging operations.

The total 2,000-hectare Sohar port and industrial zone will house mega industrial facilities ranging from an oil refinery and aluminium smelter to steel mills. The zone will be one of the world's biggest greenfield petrochemical and metal-based industrial hubs. Oman Polypropylene LLC is integrated with the refinery. The project will add value to Sohar Refinery's propylene stream to produce polypropylene that can be used in an array of downstream industries.



Figure 9. Oman Polypropylene LLC Plant, Sultanate of Oman

Soil investigations have encountered loose to very loose sand and organic silt layers in a depth of approx. 6m. For the development of access roads and storage areas it was therefore required to increase the bearing capacity of the weak subgrade.

As the most economical approach, it was decided to use geogrid reinforcement to provide the required subgrade support for the expected traffic and storage loads. The aggregate base course was installed in two layers of well graded crushed granular material, each 300 mm thick. A base layer of a composite reinforcement layer together with an intermediate laid and welded geogrid reinforcement layer, both having 40 kN/m tensile strength, ensured an increased modulus of the reinforced granular layers and finally a stable platform for the planned roads and storage areas on the originally soft subgrade.



Figure 10. Installation of composite base course reinforcement

The separation geotextile component of the used composite base course reinforcement ensured the integrity of the base course by preventing fines from migrating into the aggregate layer or aggregate from being pushed into the soft subgrade. Altogether approximately 150,000 m² of the described composite reinforcement were installed in this project.

3.2 Bangunan City Hall, Brunei

During the rainy season in December 2005 heavy rainfalls created soft soil conditions at the construction site of the Bangunan City Hall in Brunei. The fully saturated clayey subgrade did not provide sufficient bearing capacity to allow access of trucks, delivering construction material to the site (see Figure 11 (left)). To prevent a complete shutdown or any delay of construction works due to a shortage of construction materials, measures were necessary which could re-establish the trafficability on site in a very short period of time. To limit the costs for the necessary ground improvement works it was finally decided to use an on site available silty & clayey cohesive fill material in combination with composite geosynthetic reinforcement, made of a laid and welded biaxial geogrid with 30 kN/m tensile strength and a 150 g/m² needlepunched nonwoven separation and filtration geotextile.



Figure 11. (left) Severe rutting in access road, (right) Improved access road condition with geocomposite

Especially where fine grained soils are used as reinforced fill on top of extremely weak soils, the stiffness of the reinforcement layer plays an important role. The high flexural rigidity of the used geocomposite provided a stable subbase for the site traffic even with the use of cohesive fill material. The possibility of using the on site available fill material reduced the overall construction costs and allowed continuous construction works without any delays. Figure 12 gives and impression of the completed project.



Figure 12. Situation at Bangunan City Hall after completed construction works

REFERENCES

- Christopher, B. R. (2008). A Laboratory Evaluation of the Performance of NAUE Secugrid Base Reinforcement Geogrids in Roadway Stabilization Applications, Alpharetta, GA, USA
- Giroud, J.P. and Noiray, L. (1981). Design of Geotextile Reinforced Unpaved Roads, J. Geotechnical Eng. Div., ASCE, Vol. 107, No. GT9, 1981, pp 1233 – 1254
- Heerten, G. and Klomp maker, J. (2007). Improving the bearing capacity of soils with geosynthetics, IS Kyushu 07, 5th International Symposium on Earth Reinforcement, Fukuoka, Japan
- Heerten, G., Klomp maker, J. and Lesny, C. (2009). Improvement of the long-term trafficability of container storage areas in harbours with composite geogrid reinforcement, Geosynthetics 2009, Salt Lake City, USA
- Tingle, J. and Jersey, S.R. (2005), Cyclic plate load testing of geosynthetic-reinforced unbound aggregate roads, Transportation Research Board: Journal of the Transportation Research Board, No. 1936, Transportation Research Board of the National Academies, Washington, D.C., pp 60-69.
- Yoder, E.J. & Witcak, M.W. (1975), Principles of Pavement Design, 2nd Edition, John Wiley and Sons, 711